



Effect of ZrO₂ Nano Particles on Mechanical and Corrosion Behaviour of Al2024 Alloy

Edward Kennedy, B. S. Sachin, M. Ramachandra,
C. A. Niranjana, N. Sriraman and Vikram Kumar S. Jain

EasyChair preprints are intended for rapid dissemination of research results and are integrated with the rest of EasyChair.

January 21, 2020

Effect of ZrO₂ Nano Particles on Mechanical and Corrosion Behaviour of Al2024 Alloy

Edward Kennedy^a, Sachin B S^b, M.Ramachandra^b, Niranjana C.A^b,
N.Sriraman^{*c}, Vikram Kumar S. Jain^d

a. K.C.G College of Technology, Chennai, Tamilnadu, India

b. BMS College of Engineering, Bengaluru, Karnataka India

c. SASTRA Deemed to be University, School of Mechanical Engineering,
Thanjavur, Tamilnadu, India

d. National Institute of Technology, Trichy, Tamilnadu, India

zac.edwin@gmail.com
niranjancaster@gmail.com
sriraman2126@gmail.com
ykjainpesit@gmail.com

Abstract

In this study, Mechanical and Corrosion behaviour of Aluminium 2024 (Al-2024) alloy reinforced with varying weight percentage (0, 2, 4 and 6%) of ZrO₂ nano particles have been investigated. The composite was prepared through stir casting route. The rockwell hardness method was used to evaluate the hardness of the composites. The Electrochemical polarization test was carried out in 3.5% NaCl solution (sea water environment) to evaluate the corrosion resistance of the alloy. The results showed that the corrosion resistance of the alloy is significantly increased in sea water environment with increasing in addition of ZrO₂ nano particles. The corrosion morphology of the samples after corrosion were examined using Scanning electron microscope.

Keywords: Al 2024, ZrO₂, Hardness, Electrochemical Corrosion.

1. Introduction

Metal matrix nano composites (MMnC) are becoming an advanced class structural material by replacing conventional metals such as steel, cast iron copper etc. Combined properties of hard ceramic particles and the matrix phase have extended the interest of MMnC in different applications such as structural, aerospace and automobile industries [1]. MMnC offers high specific strength, high specific stiffness, excellent corrosion and wear resistance, high elastic modulus etc., which makes them superior when compared to monolithic metals and alloys [2-6]. The performance of any MMnCs depends on selection of proper matrix-reinforcement

combination. Owing to their low density (2.7 g/cm^3), aluminium and aluminium alloys have gained a great attention to use in MMnCs for many engineering applications, especially where weight reduction is more concerned. Various ceramic materials such as SiC, Al_2O_3 , ZrO_2 , Y_2O_3 , B_4C etc., used as reinforcement either in micron size or nano size [7-11]. Among these ceramic materials, ZrO_2 nano particles are the most promising reinforcing agents especially suitable for anticorrosion coatings. ZrO_2 offers excellent mechanical properties, excellent wear and chemical resistance. The addition of ZrO_2 nano particles also improves overall mechanical properties of composites [12-15].

Processing of MMnC remains challenging in order to produce defect free composites and as well as to achieve desired properties. Literature have witnessed use of different processing techniques for MMnC such as stir casting, powder metallurgy, dis integrated melt deposition etc.,. Among these techniques stir casting found more suitable and effective method for producing MMnC. Despite of poor interfacial reaction between matrix and reinforcement, stir casting is considered to be the most economical due to its lower processing cost, flexibility and high production rate [16]. Therefore, In present study an attempt is made to investigate hardness and corrosion resistance of Al 2024/ ZrO_2 nano composites by varying ZrO_2 nano particles.

2. Experimental Procedure

Aluminium 2024 alloy which contains copper as a chief alloying agent was used as a matrix material. Al 2024 alloys used in the form of ingots to melt. The chemical composition of Al 2024 obtained from Atomic Absorption Spectroscopy which is given in the Table 1. ZrO_2 nano particles with 99.9% purity, spherical shape and average diameter of 50 nm were used as a reinforcement material. Fig.1 shows SEM image of zirconia nano powder which confirms the size of particles below 50 nm.

Table 1 Chemical Composition of Al 2024

Element	Cu	Mg	Mn	Fe	Zn	Al
Content %	4.3	1.4	0.3	0.5	0.5	balance

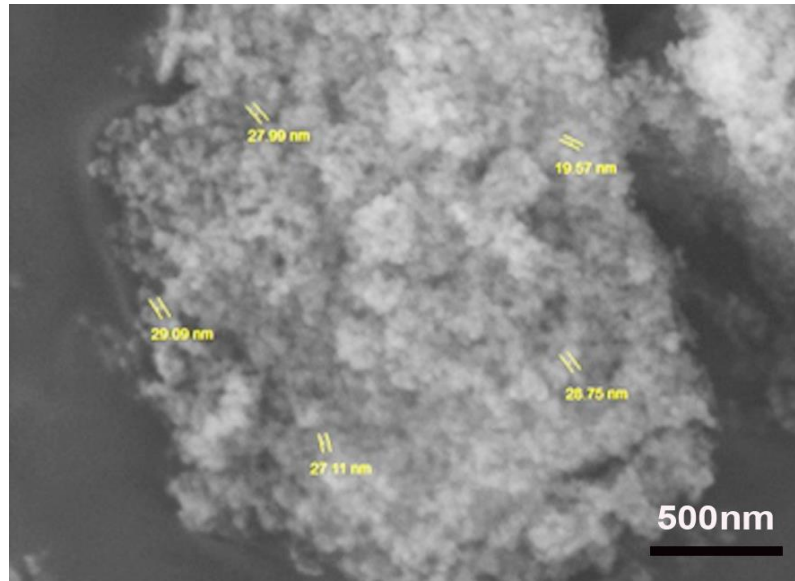


Fig. 1 SEM image of ZrO₂ nano particles

Temperature of molten alloy maintained at 800⁰C (above the melting temperature of aluminium). ZrO₂ nano particles was preheated to 300⁰C and added to molten alloy. Stirring was carried out using a steel impeller with the rotation speed of 500 rpm. The melting temperature was brought down to 650⁰C in order to homogenize the mixture and composites were poured into 350⁰C preheated mould. Composites were prepared in 3 different compositions i.e. 0%, 2%, 4% and 6% of ZrO₂ nano particles. EDS test was carried out to verify the distribution of nano particles in matrix phase. Specimens of 50 mm diameter, 30 mm length for Rockwell hardness test with 100kgf load was applied and 1/16” ball indenter was used to make the indentation. The specimen size of 25mm x 5mm x 0.8mm were prepared for Tafel polarization test. Three electrode modes in conjunction with a potentiostat were used to carry out the polarization experiments. The specimen was made as working electrode, platinum was used as counter electrode and silver/silver chloride was used as the reference electrode. 3.5% NaCl solution (sea water environment) and 3.25% NaCl + 0.25% (NH)₂SO₄ (industrial environment). SEM studies are carried out to evaluate the corrosion behaviour of the composite.

3. Results and discussions

3.1 Microstructural and Mechanical Characterization

The SEM image of 2% ZrO₂/Al₂O₃ nano composite is shown in Fig.2. It reveals uniform distribution of ZrO₂ nano particles in Al2024 aluminium alloy matrix. However, segregation

of ZrO₂ nano particles are observed in some parts due to improper dispersion caused by poor wettability of nano particles with matrix phase. The EDS was carried out to know the distribution and presence of nano particles. Intensity of the peaks in EDS confirms the presence of ZrO nano particles (Fig.2.b).

The results of the Rockwell hardness test as shown in Table 2. It clearly indicates that significant increase in hardness of MMnCs with increase in the percentage of ZrO₂ reinforcement. Hardness was increased from 70 to 80. The increase hardness is due to the inherent hard nature of the ceramic reinforcement. The reinforcement particles also act as obstacles to the movement of dislocations, which strengthens the material. Hence, with increase in the percentage of reinforcement, the material gains strength and hardness.

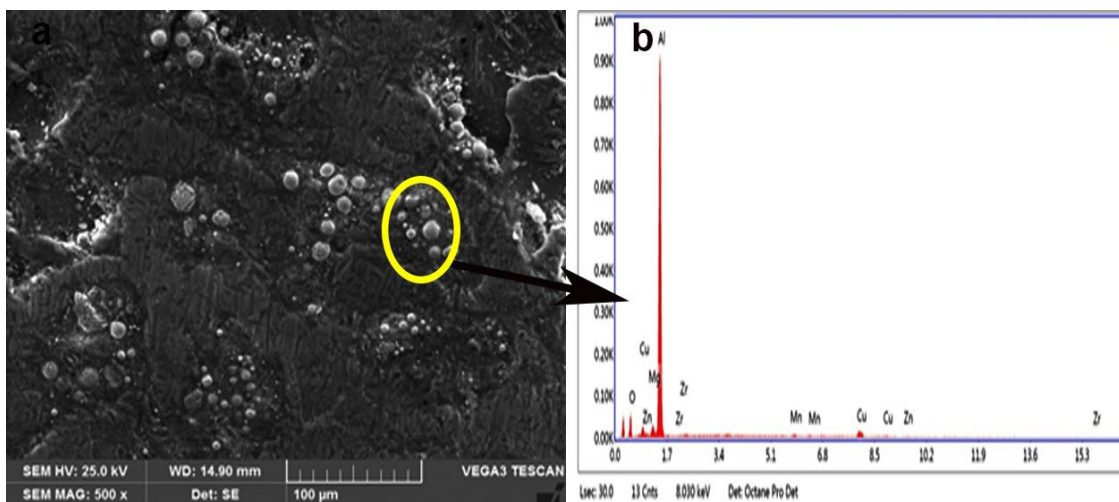


Fig. 2 (a) SEM image and (b) 2% ZrO₂/Al 2024 nano composite

Table 2 Hardness values of prepared MMnC

Sl no	% Reinforcement	Average hardness value (B scale)
1	0	70
2	2	75
3	4	78
4	6	80

3.2 Corrosion behaviour of Al2024/ZrO₂ nano composite

Fig. 3 shows Potentiodynamic polarization curve of base alloy and MMnC in sea water (NaCl) environment. Table 3 shows the values of corrosion potential, corrosion density and corrosion

rate derived from tafel fit. It is observed that corrosion potential was shifted from 0.719V to -0.745V and current potential decreased with increasing the percentage of ZrO₂. This clearly authenticates that adding of ZrO₂ nano particles increases the corrosion resistance than the base alloy.

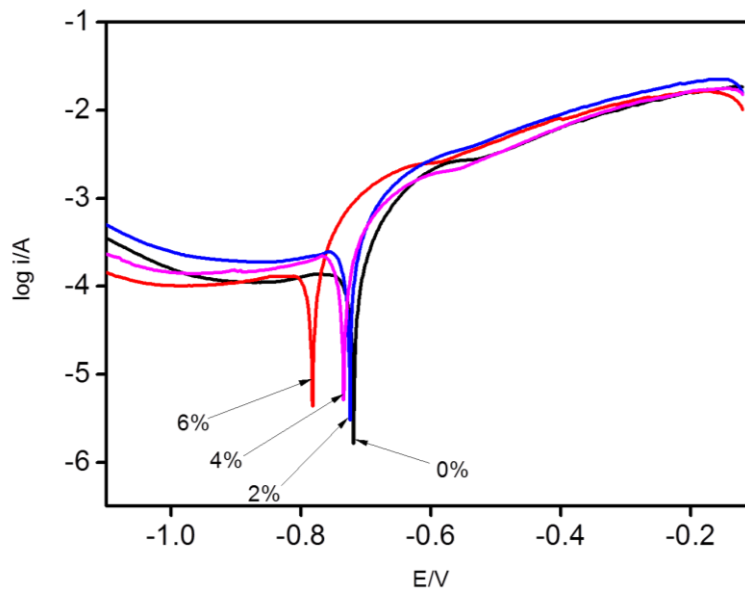


Fig. 3 Potentiodynamic polarization curve of base alloy and MMnC in sea water environment

Table 3 Data derived from Tafel fit of MMCs in NaCl electrolyte

Sl no.	% Reinforcement	Corrosion potential(V)	Corrosion current density (A/cm ²)	Corrosion Rate mm/yr
1	0	-0.719	5.79	0.18
2	2	-0.735	5.52	0.15
3	4	-0.752	5.36	0.12
4	6	-0.745	5.29	0.10

This is due to the fact that the reinforcement is a ceramic, which is a passive material. Also, the particles of the reinforcement locally prevent exposure of the metallic surface to corrosion environment which increases corrosion resistance.

Fig.4 shows the morphology of corroded surfaces of Al2024/ rO₂ reinforced nano composites. The Fig 4a shows the corrosion morphology of base alloy. It shows corrosion pits observed on the surfaces. The presence of discontinuity like porosity which acts as the starting point for pitting corrosion. Thus results in the production of positive ions in the pit which tends to attract the negative ions from the electrolyte. This leads to formation of Aluminium chloride molecule in the pit at a fast rate due to which corrosion takes place rapidly leading to dissolution of the metal. Fig 4d shows the uniform corrosion resistance. Thus adding of ZrO₂ oxide increased the corrosion resistance of the composite.

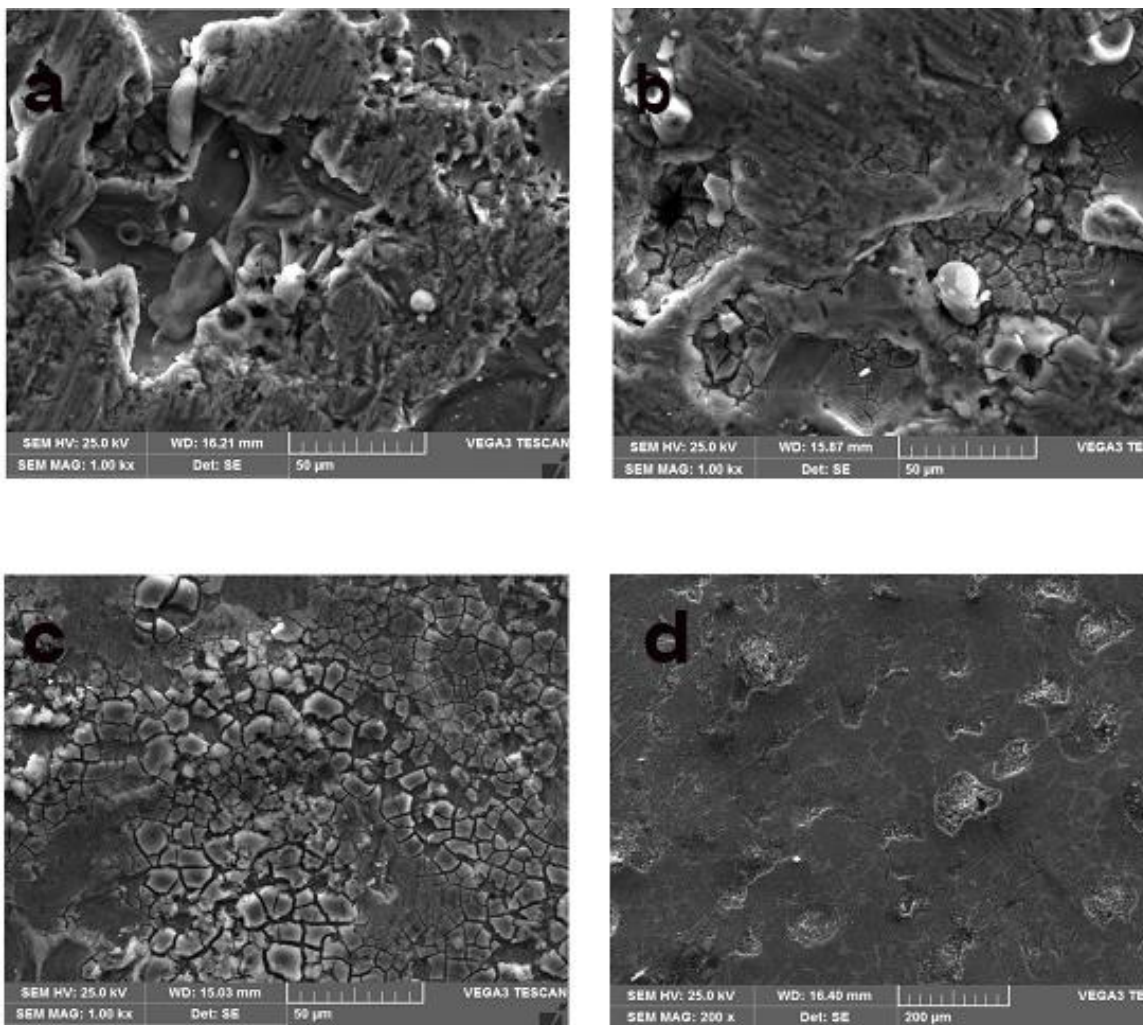


Fig 4 a) base alloy b) 2% ZrO₂ c) 4% ZrO₂ d) 6% ZrO₂

Conclusion

- Al 2024/ZrO₂ nano composites are fabricated through stir casting technique. Distribution of nano particles found uniform however formation of clusters was observed at some portions.
- Hardness of the composites found higher compared to base alloy. Hardness increased with increase in percentage of nano particles.
- In salt water environment (3.5% NaCl), the adding of ZrO₂ nano composites increases the corrosion resistance of the composite. Thus ZrO₂ reinforcement has a positive impact on improving the corrosion resistance in the case of pitting corrosion prevalent in sea water.

References

- [1] D.B. Miracle, Metal matrix composites – From science to technological significance, *Composites Science and Technology*, 65(2005) 2526-2540
- [2] Riccardo Casati and Maurizio Vedani , Metal Matrix Composites Reinforced by Nano-Particles—A Review, *Metals* , 4(1) (2014) 65-83
- [3] M. Sabzi, S.M. Mirabedini, J. Zohuriaan-Mehr, M. Atai, Surface modification of TiO₂ nano-particles with silane coupling agent and investigation of its effect on the properties of polyurethane composite coating, *Prog. Org. Coat.* 65 (2009) 222–228.
- [4] Fei He , Qingyou Han , Mark J. Jackson , Nanoparticulate reinforced metal matrix nanocomposites – a review, *International Journal of Nanoparticles* 1(4) (2008)
- [5] I. J. Shon and H. S. Kang, “Properties and fast low-temperature consolidation of nanocrystalline Ni–ZrO₂ composites by high frequency induction heated sintering,” *Journal of Alloys and Compounds*, vol. 509, pp. 2964–2969, 2011.
- [6] C. Suryanarayana, “Synthesis of nanocomposites by mechanical alloying,” *Journal of Alloys and Compounds*, vol. 509, supplement 1, pp. S229–S234, 2011.
- [7] Yaping Zheng, Ying Zheng, Rongchang Ning, Effects of nanoparticles SiO₂ on the performance of nanocomposites *Materials Letters* 57 (2003) 2940–2944

- [8] Ali Mazahery and Mohsen Ostadshabani Investigation on mechanical properties of nano-Al₂O₃-reinforced aluminum matrix composites, *JOURNAL OF COMPOSITE MATERIALS*, 45(24) (2011) 2579–2586
- [9] C. I. Chang , Y. N. Wang, H. R. Pei, C. J. Lee , X. H. Du , J. C. Huang Microstructure and ‘Mechanical Properties of Nano-ZrO₂ and Nano-SiO₂ Particulate Reinforced AZ31-Mg Based Composites Fabricated by Friction Stir Processing’ *Key Engineering Materials* Vol. 351 (2007) pp. 114-119
- [10] M. Khakbiz, F. Akhlaghi ‘Synthesis and structural characterization of Al–B₄C nano-composite powders by mechanical alloying’ *Journal of Alloys and Compounds* 479 (2009) 334–341
- [11] Hafeez Ahamed, V. Senthilkumar, Consolidation behavior of mechanically alloyed aluminum based nanocomposites reinforced with nanoscale Y₂O₃/Al₂O₃ particles, *Materials Characterization*, Volume 62, Issue 12, (2011) 1235-1249,
- [12] S. Kozhukharov, G. Tsaneva, V. Kozhukharov, J. Gerwann, M. Schem, T. Schmidt, M. Veith, Corrosion protection properties of composite hybrid coatings with involved nanoparticles of zirconia and ceria, *J. Univ. Chem. Technol.* 43 (2008) 73–80.
- [13] G. Gusmano, G. Montesperelli, M. Rapone, G. Padeletti, A. Cusmà, S. Kaciulis, A. Mezzi, R. Di Maggio, Zirconia primers for corrosion resistant coatings, *Surf. Coat. Technol.* 201 (2007) 5822–5828.
- [14] J.F. Quinson, C. Chino, A.M. De Becdelievre, C. Guizard, M. Brunel, Deformation capability and protective role of zirconia coatings on stainless steel, *J. Mater. Sci.* 31 (1996) 5179–5184.
- [15] M. Behzadnasab , S.M. Mirabedini, K. Kabiri and S. Jamali Corrosion performance of epoxy coatings containing silane treated ZrO₂ nanoparticles on mild steel in 3.5% NaCl solution, *Corrosion Science*, 53 (2011) 89–98
- [16] L. Ceschini et al., Aluminum and Magnesium Metal Matrix Nanocomposites, *Engineering Materials*, DOI 10.1007/978-981-10-2681-2_2